

Natural Pozzolan as a Partial Substitute for Cement in Concrete

Ghassan K. Al-Chaar^{1,*}, Mouin Alkadi² and Panagiotis G. Asteris³

¹Research and Development Center (ERDC), Construction Engineering Research Laboratory, Champaign, IL, USA;

²Techno Advanced Building Material Company, Damascus Road, Sweda, Syria; ³Computational Mechanics Laboratory, School of Pedagogical and Technological Education, 141 24 Heraklion, Athens, Greece

Abstract: In this paper, the use of natural pozzolan as a partial cement substitute in concrete materials is investigated. By means of a test series, four mixes using three types of natural pozzolan, as well as a Class F fly ash, are evaluated. The effectiveness of each pozzolan in controlling alkali-silica reactions has been studied. Correlations have been revealed between the mechanical properties of the proposed mixes and a Portland cement control mix. The results are also compared with industry standards for mortars made with fly ash and silica fume. The paper's findings indicate that one type of pozzolan may be used as a substitute for fly ash, but not for silica fume.

Keywords: Natural pozzolan, cement replacement, concrete, mortar, fly ash, mechanical properties, silica fume.

1. INTRODUCTION

Under the strong contemporary demand for modern and environmentally friendly materials, natural pozzolan can be proved to be such a material and several researchers have focused their research efforts in using it as a partial substitute in the manufacture of concrete and mortar [1-10].

Pozzolans are divided into two categories, namely the natural and the artificial, as metakaoline and silica fume (SF). In recent years, the industry has shifted to using natural pozzolans because of their lower cost and accessibility. A pozzolan is a siliceous material that can be used as an inexpensive substitute for cement in mortar mixtures. Pozzolans participate in a cementitious reaction with calcium hydroxide (i.e., lime) and other alkalis. Pozzolans are effective at lowering the mortar's heat of hydration, which improves its workability and durability. They can also improve concrete and mortar resistance to both sulfate attack and the alkali-silica reaction (ASR), which makes it beneficial to use in large concrete projects such as bridges and dams (Gibbons 1997 [11], Tsimas *et al.* 2005 [12], Hossain and Mol 2011 [8]), as well as in the restoration of historic and monumental masonry structures as a restoration mortar (Moropoulou *et al.* 1998 [13], 2004 [14] and 2005 [15], Asteris *et al.* 2005 [16]).

Major sources of natural and manmade pozzolans include volcanic mineral deposits, fired and crushed clay, and fly ash, which is created during the burning of coal for power generation (Gibbons 1997 [11]). Most pozzolans are profuse, but current uses for them are limited. Consequently, they represent a potential source of inexpensive construction material.

This paper investigates the feasibility and effectiveness of using naturally occurring pozzolan materials as an additive or substitute for cement in concrete mixtures. This investigation has been carried out through a series of experiments using a Class F fly ash and three types of natural pozzolans under the following laboratory tests: chemical composition, moisture content, loss on ignition, compressive strength, strength activity index, expansion from alkali-silica reaction (ASR), heat of hydration, slump, drying shrinkage, and autoclave expansion.

2. LITERATURE REVIEW

Alkalis in cement (typically calcium hydroxide and sodium and potassium oxide) can react with aggregates containing reactive silica or carbonate mineral constituents. In cured cement, these reactions produce different types of expansion that can cause concrete deterioration through internal cracking, surface cracking, and/or aggregate pop-out (Dolar-Mantuani 1983 [17]). Classic research by Stanton (1940) [18] ascribed ASR degradation to an expansive chemical reaction between the alkalis contained in the cement paste and certain reactive forms of silica within aggregate. Stanton identified opal and chert as common forms of reactive silica.

Pozzolans as an additive reduce cracking and expansion that results from ASR. The ASR is known to be normally occurs from the following combination of conditions (Hobbs 1988 [19]):

1. significant quantity of reactive silica.
2. reactive silica within a critical range of proportions.
3. available alkalis above a critical level.
4. water from an external source.

Suitable precautions must be taken to minimize or eliminate harmful expansion and cracking, such as:

- decreasing the amount of reactive aggregate (Björk 2002 [20]).

*Address correspondence to this author at the Construction Engineering Research Laboratory, Champaign, IL, USA;
Tel: 217-373-7247; Fax: 217-722-3320;
E-mail: ghassanalchaar@yahoo.com

- using low-alkali cement as per ASTM C150-09 [21].
- using mineral admixtures such as pozzolans or blast furnace slag (Lane *et al.* [22]; Wang and Gillott 1993 [23]; Thomas and Innis 1998 [24]).
- reducing the availability of water such that the relative humidity in concrete pores falls below about 85–90%.

In mass and high-strength concrete, the production of heat during the hydration reaction creates thermal gradients which can induce cracking in hardening concrete (Yeon *et al.* 2012 [25], De Schutter 2002 [26]). Thermal cracking can be mitigated by reducing the heat of hydration, a goal which can be achieved through the use of pozzolans or ground, granulated blast furnace slag (Tokyay *et al.* 2012 [27], Nili and Salehi 2010 [28]).

3. CHARACTERISTICS OF CONCRETE FORMULATED WITH POZZOLAN ADDITIVES

3.1. Concrete Formulation Components

3.1.1. Cementitious Materials

For this investigation, pozzolanic materials were selected which conformed to ASTM C618-00 [29]. Natural pozzolan was used from Saudi Arabia (Pozzolan S1), South Africa (Pozzolan S2), and Jordan (Pozzolan J). This phase of testing also included a Class F fly ash, whose properties are specified in ASTM C618-00 [29].

The natural pozzolan samples were crushed, ground, and tested. A Cilas Granulometre 715 device was used to determine the grain size distributions of the materials. Type I Portland cement was used in the production of concrete mixes. Chemical properties of the cement were tested periodically in the laboratory. (Table 1) shows chemical composition, loss on ignition, density, and fineness of all cementi-

tious materials, while (Fig. 1) shows their particle size distributions.

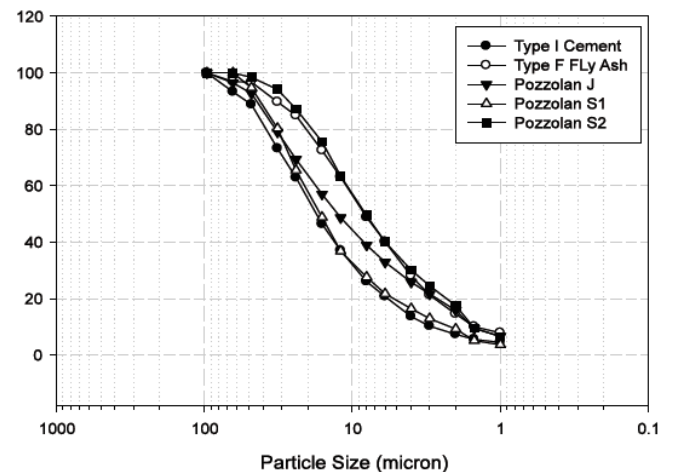


Fig. (1). Particle size distribution of cementitious materials.

3.1.2. Aggregate Materials

Washed, surface-dry basalt aggregates were used in this study. Fine aggregate, consisting of crushed basalt rocks, was sifted, washed over a #100 (150 μm) sieve with a water spray, and re-graded to the final, desirable particle size distribution. Grain size distributions for all aggregates are shown in (Fig. 2). Coarse aggregates were used for slump testing, only.

3.2. Compressive Strength Testing

This investigation used test procedures outlined by ASTM C109/C109M-08 [30] to evaluate the effect of replacing Portland cement with different pozzolanic materials on

Table 1. Analysis of Cementitious Materials

Determinate	Portland cement	Fly Ash	Pozzolan J	Pozzolan S1	Pozzolan S2
SiO ₂ (%)	20	51.06	42.56	48.44	44.7
Al ₂ O ₃ (%)	5.68	32.23	13.55	15.97	14.5
CaO (%)	64.94	4.18	9.75	8.53	9
Fe ₂ O ₃ (%)	3.98	3.42	13.24	13.2	11.8
MgO (%)	0.7	1.06	11.15	7.89	7.8
SO ₃ (%)	2.81	0.42	0.35	0.1	0.15
Other (%)	1.89	7.63	9.4	5.87	12.05
Water Requirement (%)	-	90	100	100	100
Free Water (%)	-	0.1	0.1	0.1	0.1
Loss on Ignition (%)	1.16	0.81	2.56	1.26	1.5
Insoluble Residue (%)	0.32	-	-	-	-
Blaine Fineness (m ² /kg)	320	238	461	320	564
Density (g/cm ³)	-	2.2	2.86	2.8	2.8

hydration at a given temperature. The most common method of determining the heat of hydration is described in ASTM C186-98 [37], Standard Test Method for Heat of Hydration of Hydraulic Cement. It is accomplished by measuring the heat of solutions of unhydrated and hydrated cement in a mixture of nitric and hydrofluoric acids. The difference between the two values represents the heat of hydration.

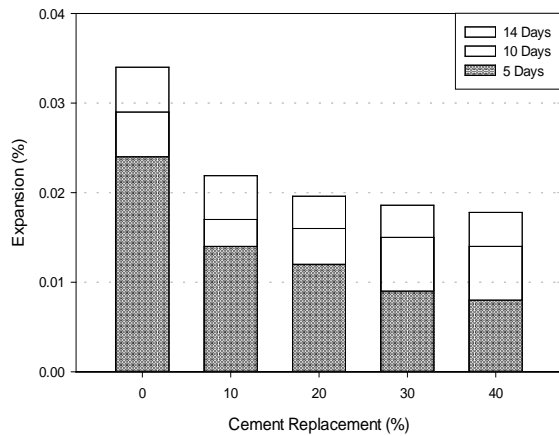


Fig. (8). Effect of cement replacement with fly ash on ASR expansion.

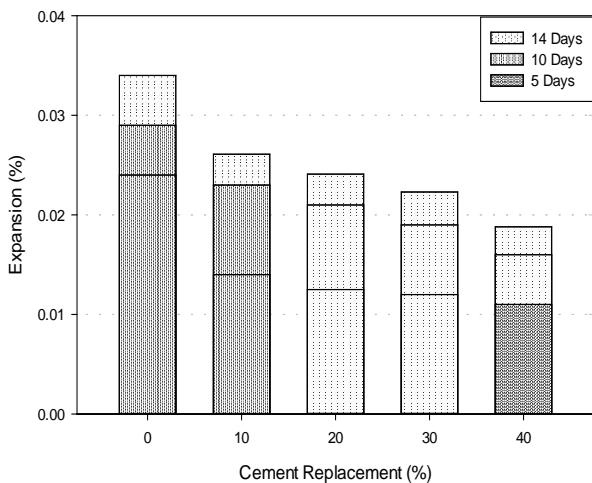


Fig. (9). Effect of cement replacement with Pozzolan J on ASR expansion.

This method was used to calculate the heat of hydration for one Portland cement control mixture and two test mixtures incorporating fly ash and Pozzolan S1. The results at curing durations of 1, 3, 7, 14, and 28 days are shown in (Fig. 11). This test series determined that the Pozzolan S1 mixture produced about 15% less heat of hydration than the fly ash mixture, where the fly ash mixture produced about 30% less heat of hydration than the control mixture.

3.6. Effect of Pozzolan and Water-to-Cement Ratio on Slump

Ten 2-inch cube specimens were prepared with varying amounts of Pozzolan S1 (between 0 and 30%), and water-to-cement (W/C) ratios varying between 0.456 and 0.5. (Table 2) displays two slump testing mixture examples: a control

mix and a 10% pozzolan mix. The slumps of nine specimens at 0, 30, and 45 minutes are shown in (Fig. 12). The results in (Fig. 12) show that increasing the amount of pozzolan generally increased the slump and workability of these specimens. In five specimens, the amount of pozzolan also varied between 10% and 30%, but the W/C ratios were decreased. As expected, reducing the W/C ratio reduced the slump of the specimens.

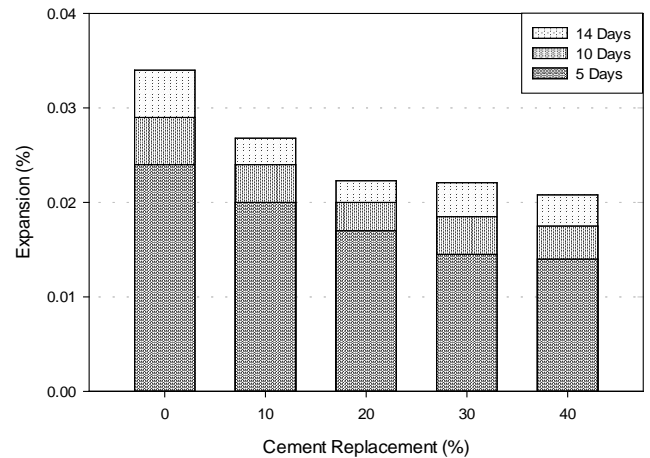


Fig. (10). Effect of cement replacement with Pozzolan S1 on ASR expansion.

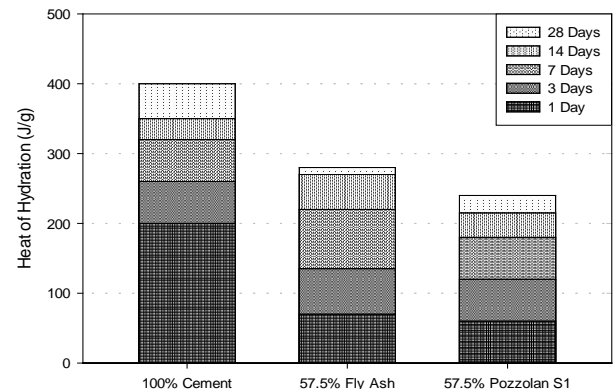


Fig. (11). Effect of various pozzolans on heat of hydration.

3.7. Effect of Pozzolan and Water-to-Cement Ratio on Strength

Specimens with varying amounts of Pozzolan S1 and W/C ratios were tested in compression after 7 and 28 days to determine the effect of the pozzolan and W/C ratio on the early compressive strength. The results of these tests are shown in (Fig. 13).

Activity indexes are calculated by dividing the specimen strength by the strength of a control specimen at the same age and multiplying by 100%. The results in (Fig. 14) show that increasing the percentage of pozzolan generally decreases the activity index.

Three mixes were designed with 20% pozzolan, but each used pozzolan of a different fineness. As shown in (Fig. 15),

the early compressive strengths of these specimens increased with increasing pozzolan fineness.

Table 2. Mixture for Control Specimens

Test Mixes			
Pozzolan replacement		0%	10%
Total Volume (m ³)		0.03	0.03
W/c		0.5	0.45
Ingredients			
O. P. C.	kg	10.5	8.4
Pozzolan	"	0	2.1
3/4"	"	22.35	22.92
3/8"	"	13.08	13.41
F. Sand	"	19.08	19.56
Free water	L	5.25	4.719
Total water	"	5.652	5.139
Pr - 150	"	0.063	0.063
Slump (mm)			
Initial		170	50
30 min		120	-
45 min		105	-
60 min		95	-
Temperature (°C)			
Water		16	16
Ambient		15	16.8
Concrete(i)		20.5	20
Concrete(f)		19.5	-

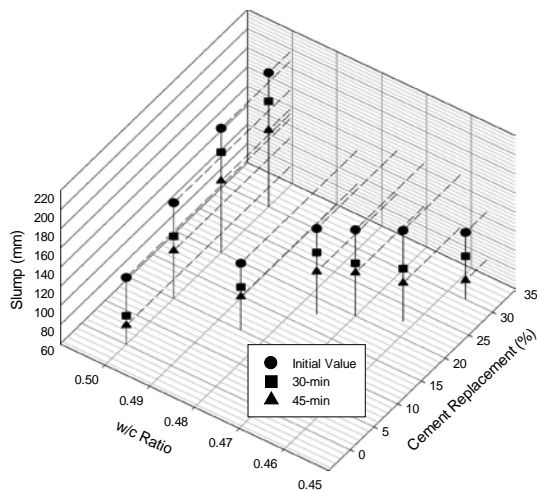


Fig. (12). Slump versus W/C-ratio and cement replacement with Pozzolan S1.

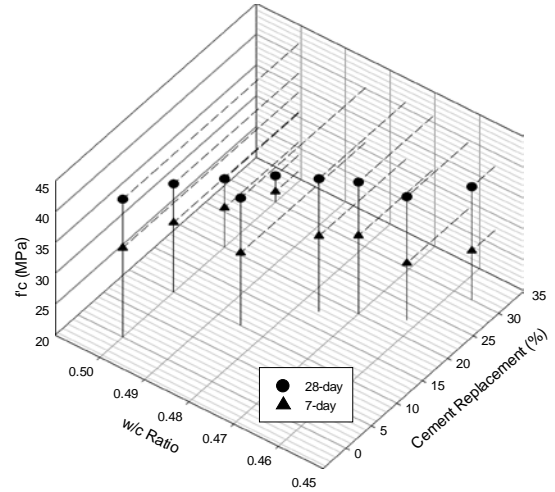


Fig. (13). Strength versus W/C-ratio and cement replacement with Pozzolan S1.

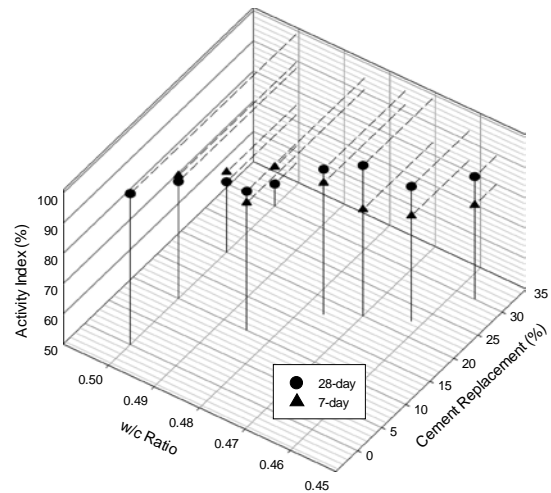


Fig. (14). Activity index versus W/C and cement replacement with Pozzolan S1.

4. COMPARISON OF POZZOLAN S1 WITH ASTM SPECIFICATIONS FOR FLY ASH AND SILICA FUME

The properties of 20-micron fine natural Pozzolan S1 were investigated and compared with the ASTM specifications for fly ash and silica fume to determine the extent of their similarity. The following ASTM specifications were used as reference standards:

- ASTM C618-00 [29], Standard Specification for Coal Fly Ash and Raw or Calcined Natural Pozzolan for Use as a Mineral Admixture in Concrete.

- ASTM C1240-00 [38], Standard Specification for use of Silica Fume as a Mineral Admixture in Hydraulic Cement Concrete Mortar and Grout.

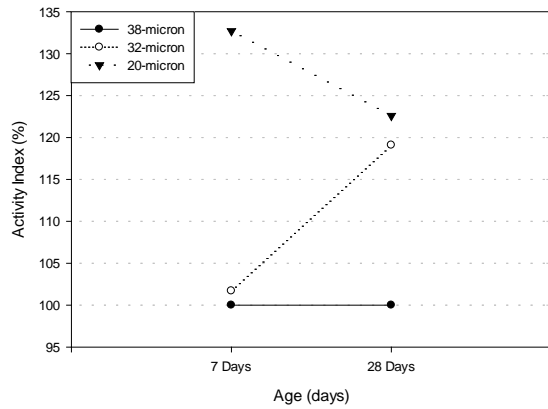


Fig. (15). Effect of Pozzolan S1 fineness on activity index (20% replacement).

4.1. Physical Tests

The following physical tests were conducted on the pozzolan specimens:

- strength activity index (ASTM C311-00 [33]).
- density (ASTM C188-95 [39]).
- fineness per sieve analysis (ASTM C311-00 [33]).
- Blaine fineness (ASTM C204-00 [40]).
- increase in drying shrinkage (ASTM C157 [41]).
- expansion stability using autoclave (ASTM C157-08 [42]).

Two types of specimens were used: (1) a control specimen with 100% Portland cement and sand and (2) an activity specimen with 80% cement, 20% natural Pozzolan S1, and sand. The chemical composition and physical properties of the control specimen were used for comparison with the activity specimen. The results of the physical tests are shown in (Table 3 and Table 4).

Table 3. Strength Activity Index Results

Property	Control specimen	Activity specimen
Shear Strength at 7 days (N/mm ²)	29.5	22.6
Strength Activity Index at 7days,%	76.6	
Shear Strength (N/mm ²) at 28 days	36.0	28.0
Strength Activity Index at 28 days,%	77.8	

Table 4. Density, Fineness, Dry Shrinkage, and Volume Stability

Physical Property		Results
Density		2.83 g/cm ³
Fineness	Sieve analysis	10.8%
	Blaine	359 m ² /kg
Increase in drying shrinkage after 28 days		-0.009% *
Volume stability (autoclave expansion / contraction)		0.2%

* The ASTM standard specifies to add (-) sign if the dry shrinkage rate of control specimens is greater than the tested specimens

4.2. Chemical Tests

Chemical analysis of the specimens was conducted to determine the effectiveness of the natural pozzolan in contributing to sulfate resistance. The results of the chemical analysis are given in (Table 5 and Table 6).

Table 5. Chemical Composition

Chemical Composition,%	Control Cement	Natural Pozzolan S1
SiO ₂	19.26	48.44
CaO	63.34	8.53
Fe ₂ O ₃	3.6	13.3
Al ₂ O ₃	5.35	15.97
MgO	2.36	7.98
SO ₃	2.48	0.1
K ₂ O	0.51	1.37
Cl	0.011	0.012

Table 6. Chemical Properties

Property	Control Cement	Natural Pozzolan S1
Loss on Ignition,%	2.35	1.26
Moisture Content,%	-	0.34
PH	-	9.0
Carbon Content,%	-	0.33
Insoluble Residue,%	0.74	-

4.3. Physical Analysis

The physical properties of the natural pozzolan specimens are compared with the ASTM requirements for fly ash and silica fume in (Table 7). As shown in this table, the natural pozzolan specimens met the requirements for fly ash but

Table 7. Comparison Between Pozzolan Physical Properties and ASTM Requirements

Test	Results for Pozzolan S1	ASTM C618-00 Class N Pozzolan, Class F and C Fly Ash [29]	ASTM C1240-00 Silica Fume [38]
Blaine Fineness (m ² /kg)	359	-	15 (min.)
Pct. wt. remaining on 45-micron sieve	10.8	34 (max.)	10 (min.)
Strength Activity Index at 7 days,%	76.6	75 (min.)	85 (min.)
Strength Activity Index at 28 days,%	77.8	75 (min.)	-
Autoclave expansion/contraction,%	0.02	0.8 (max.)	-
Pct. Drying Shrinkage at 28 days	-0.009	0.03 (max.)	-

not for silica fume. The fineness values were less than 34%, and the strength activity indexes were greater than 75%. Their volume stabilities were less than 0.8%, and the increase in drying shrinkage at 28 days was less than 0.03%. While the natural pozzolan met the silica fume requirements for Blaine fineness and the percentage remaining on the 45 micron sieve, it is significant that it did not meet the 7-day strength activity index of 85%. The reason may be attributed to the Silica fume ultrafine material with spherical particles less than 1 μ m in diameter being much less than the size of natural pozzolan.

4.4. Chemical Analysis

The chemical test results for the natural pozzolan specimens were compared with the ASTM requirements, as shown in (Table 8). The natural pozzolan specimens met all requirements for fly ash but did not meet the 85% silicon dioxide requirement for silica fume. It is worth noting that the ASTM specification for class F fly ash requires the sum of Fe₂O₃, Al₂O₃, and SiO₂ to be at least 70%. It also specifies SO₃ less than 5%, moisture content less than 3%, and loss on ignition less than 6%. Therefore, natural pozzolan behaves more as a fly ash than a silica fume.

5. CONCLUDING REMARKS

From the previous results we can conclude that:

- At the early ages, the strength activity index of fly ash due to packing effect is higher than due to pozzolanic reaction.

- Pozzolan S1 can provide a satisfactory substitute for fly ash and other natural pozzolans as tested against ASTM C618-00 [29]. It was clearly found to be effective in controlling ASR. It also produces about 15% less heat of hydration than Class F fly ash, whereas Class F fly ash produces about 30% less heat of hydration than Portland cement only.
- Pozzolan specimens ground to a size of 20 microns meet the chemical and physical requirements for fly ash. The fineness values were less than 34%, and the strength activity indexes at 7 and 28 days were greater than 75%. Volume stabilities were less than 0.8%, and the increase in drying shrinkage at 28 days was less than 0.03%. The percentage of total iron oxide, aluminum oxide, and silicon dioxide was greater than 70%. The percentage of sulfur trioxide was less than 5%. Moisture content was less than 3%. Loss on ignition was less than 6%.
- The chemical and physical properties of Pozzolan S1 are comparable to fly ash, and the one can be substituted for the other.

It should be mentioned that Pozzolan S1 did not meet the ASTM C1240-00 [38] chemical and physical requirements for silica fume. Its strength activity index at 7 days was less than 85%, and the percentage of silicon dioxide was not met. However, it met the requirements for the percentage remaining on the 45 micron sieve at greater than 10%, moisture content less than 3%, loss on ignition less than 6%, and Blaine fineness greater than 15 m²/kg.

Table 8. Comparison Between Pozzolan Properties and ASTM Requirements

Test	Results for Pozzolan S1	ASTM C618-00 [29]			
		Natural Pozzolan Class N	Fly ash		Silica fume
			Class F	Class C	
Fe ₂ O ₃ + Al ₂ O ₃ + SiO ₂ (%)	77.61	70 (min.)	70 (min.)	50 (min.)	-
SO ₃ (%)	0.34	4 (max.)	5 (max.)	5 (max.)	-
Moisture content (%)	0.1	3 (max.)	3 (max.)	3 (max.)	-
Loss on ignition (%)	1.26	10 (max.)	6 (max.)	6 (max.)	6 (max.)
SiO ₂ (%)	48.44	-	-	-	85 (min.)

Based on the above findings, it is concluded that Pozzolan S1 is not a suitable replacement for ASTM C1240-00 [38] silica fume despite meeting the requirements for fineness, moisture content, and loss on ignition.

CONFLICT OF INTEREST

The author(s) confirm that this article content has no conflicts of interest.

ACKNOWLEDGEMENT

The authors would like to acknowledge the assistance of Kevin O'Connor, a civil engineering graduate student at the University of Illinois, Urbana-Champaign. The authors are also grateful to Miltiadis Chronopoulos, Research Associate at the National Technical University of Athens, and Adamantia Athanasopoulou, Programme Leader, Faculty of Engineering, Metropolitan College, Athens, Greece for their helpful discussions and suggestions.

REFERENCES

- [1] B. B. Sabir, S. Wild, and J. Bai, "Metakaolin and calcined clays as pozzolans for concrete: a review", *Cement and Concrete Composites*, vol. 23, no. 6, pp. 441-454, 2001.
- [2] H. Binici, O. Aksogan, I. H. Cagatay, M. Tokyay, and E. Emsen, "The effect of particle size distribution on the properties of blended cements incorporating GGBFS and natural pozzolan (NP)", *Powder Technology*, vol. 177, no. 3, pp. 140-147, 2007.
- [3] A. Cavdar, and S. Yetgin, "Availability of tuffs from northeast of Turkey as natural pozzolan on cement, some chemical and mechanical relationships", *Construction and Building Materials*, vol. 21, no. 12, pp. 2066-2071, 2007.
- [4] S. K. Antiohos, A. Papageorgiou, V. G. Papadakis, and S. Tsimas, "Influence of quicklime addition on the mechanical properties and hydration degree of blended cements containing different fly ashes", *Construction and Building Materials*, vol. 22, no. 6, pp. 1191-1200, 2008.
- [5] E. Badogiannis, and S. Tsvivilis, "Exploitation of poor Greek kaolins: Durability of metakaolin concrete", *Cement and Concrete Composites*, vol. 31, no. 2, pp. 128-133, 2009.
- [6] G. Mertens, R. Snellings, K. Van Balen, B. Bicer-Simsir, P. Verlooy, and J. Elsen, "Pozzolanic reactions of common natural zeolites with lime and parameters affecting their reactivity", *Cement and Concrete Research*, vol. 39, no. 3, pp. 233-240, 2009.
- [7] A. R. Pourkhorshidi, M. Najimi, T. Parhizkar, F. Jafarpour, and B. Hillemeier, "Applicability of the standard specifications of ASTM C618 for evaluation of natural pozzolans", *Cement and Concrete Composites*, vol. 32, no. 10, pp. 794-800, 2010.
- [8] K. M. A. Hossain, and L. Mol, "Some engineering properties of stabilized clayey soils incorporating natural pozzolans and industrial wastes", *Construction and Building Materials*, vol. 25, no. 8, pp. 3495-3501, 2011.
- [9] Y. Senhadji, G. Escadeillas, H. Khelafi, M. Mouli, and A. S. Benosman, "Evaluation of natural pozzolan for use as supplementary cementitious material", *European Journal of Environmental and Civil Engineering*, vol. 16, no. 1, pp. 77-96, 2012.
- [10] M. Valipour, F. Pargar, M. Shekarchi, and S. Khani, "Comparing a natural pozzolan, zeolite, to metakaolin and silica fume in terms of their effect on the durability characteristics of concrete: A laboratory study", *Construction and Building Materials*, vol. 41, pp. 879-888, 2013.
- [11] P. Gibbons, "Pozzolans for Lime Mortars", *The Conservation and Repair of Ecclesiastical Buildings*, 1997. [Online] available: <http://www.buildingconservation.com/articles/pozzo/pozzo.htm>.
- [12] S. Tsimas, and A. Moutsatsou-Tsima, "High-calcium fly ash as the fourth constituent in concrete: Problems, solutions and perspectives", *Cement and Concrete Composites*, vol. 27, no. 2, pp. 231-237, 2005.
- [13] A. Moropoulou, P. Maravelaki-Kalaitzaki, M. Borboudakis, A. Bakolas, P. Michailidis, and M. Chronopoulos, "Historic mortars technologies in Crete and guidelines for compatible restoration mortars", *PACT: Journal of the European Study Group on Physical, Chemical, Biological and Mathematical Techniques Applied to Archaeology*, vol. 55, pp. 55-72, 1998.
- [14] A. Moropoulou, A. Bakolas, and E. Aggelakopoulou, "Evaluation of pozzolanic activity of natural and artificial pozzolans by thermal analysis", *Thermochimica Acta*, vol. 420, no. 1-2, pp. 135-140, 2004.
- [15] A. Moropoulou, A. Bakolas, and S. Anagnostopoulou, "Composite materials in ancient structures", *Cement and Concrete Composites*, vol. 27, no. 2, pp. 295-300, 2005.
- [16] P. G. Asteris, A. D. Tzamtzis, P. P. Vouthouni, and D. S. Sophianopoulos, "Earthquake Resistant Design and Rehabilitation of Masonry Historical Structures", *Practice Periodical on Structural Design and Construction*, American Society of Civil Engineers (ASCE), vol. 10, no. 1, pp. 49-55, 2005.
- [17] L. Dolari-Mantuani, *Handbook of Concrete Aggregates, A Petrographic and Technological Evaluation*, Noyes Data Corporation, United States, pp. 79-125, 1984.
- [18] T. E. Stanton, "Expansion of concrete through reaction between cement and aggregate", *Proceedings of the American Society of Civil Engineers*, vol. 66, no. 10, pp. 1781-1811, 1940.
- [19] D. W. Hobbs, *Alkali-Silica Reaction in Concrete*, Thomas Telford, London, 1988.
- [20] F. Björkand, and C. A. Eriksson, "Measurement of alkalinity in concrete by a simple procedure, to investigate transport of alkaline material from the concrete slab to a self-levelling screed", *Construction and Building Materials*, vol. 16, no. 8, pp. 535-542, 2002.
- [21] ASTM Standard C150-09, *Standard Specification for Portland Cement*, ASTM International, West Conshohocken, PA, 2009.
- [22] R. O. Lane, and J. F. Best, "Properties and use of fly ash in Portland cement concrete", *Concrete International*, vol. 4, no. 7, pp. 81-92, 1982.
- [23] H. Wang, and J. E. Gillott, "Effect of Three Zeolite-containing Natural Pozzolanic Materials on Alkali-Silica Reaction", *Cement, Concrete, and Aggregates*, vol. 15, no. 1, pp. 24-30, 1993.
- [24] M. D. A. Thomas, and F. A. Innis, "Use of the Accelerated Mortar-Bar Test for Evaluating the Efficacy of Mineral Admixtures for Controlling Expansion Due to Alkali-Silica Reaction", *Cement, Concrete and Aggregates*, vol. 21, no. 2, pp. 157-164, 1999.
- [25] J. H. Yeon, S. Choi, and M. C. Won, "In situ measurement of coefficient of thermal expansion in hardening concrete and its effect on thermal stress development", *Construction and Building Materials*, vol. 38, pp. 306-315, 2013.
- [26] G. De Schutter, "Finite element simulation of thermal cracking in massive hardening concrete elements using degree of hydration based material laws", *Computers and Structures*, vol. 80, no. 27-30, pp. 2035-2042, 2002.
- [27] M. Tokyay, T. Delibas, and I. O. Yaman, "Heat of Hydration of GGBFS and Natural Pozzolan Incorporated Cements", *Cement & Concrete World*, vol. 17, no. 95, p. 72, 2012.
- [28] M. Nili, and A. M. Salehi, "Assessing the effectiveness of pozzolans in massive high-strength concrete", *Construction and Building Materials*, vol. 24, no. 11, pp. 2108-2116, 2010.
- [29] ASTM Standard C618-00, *Specification for Coal Fly Ash and Raw or Calcined Natural Pozzolan for Use as a Mineral Admixture in Portland Cement Concrete*, ASTM International, West Conshohocken, PA, 2000.
- [30] ASTM Standard C109/C109M-08, *Test Method for Compressive Strength of Hydraulic Cement Mortars (Using 2-in. or 50-mm Cube Specimens)*, ASTM International, West Conshohocken, PA, 2008.
- [31] ASTM Standard C778-06, *Standard Specification for Standard Sand*, ASTM International, West Conshohocken, PA, 2006.
- [32] ASTM Standard C305-06, *Standard Practice for Mechanical Mixing of Hydraulic Cement Pastes and Mortars of Plastic Consistency*, ASTM International, West Conshohocken, PA, 2006.
- [33] ASTM Standard C311-00, *Standard Test Methods for Sampling and Testing Fly Ash or Natural Pozzolans for Use in Portland-Cement Concrete*, ASTM International, West Conshohocken, PA, 2000.
- [34] J. Tangpagasit, R. Cheerarot, C. Jaturapitakkul, and K. Kiattikomol, "Packing effect and pozzolanic reaction of fly ash in mortar", *Cement and Concrete Research*, vol. 35, no. 6, pp. 1145-1151, 2005.
- [35] ASTM Standard C1260-07, *Standard Test Method for Potential Alkali Reactivity of Aggregates (Mortar-Bar Method)*, ASTM International, West Conshohocken, PA, 2007.

- [36] ASTM Standard C490-08, *Standard Practice for Use of Apparatus for the Determination of Length Change of Hardened Cement Paste, Mortar, and Concrete*, ASTM International, West Conshohocken, PA, 2008.
- [37] ASTM Standard C186-98, *Standard Test Method for Heat of Hydration of Hydraulic Cement*, ASTM International, West Conshohocken, PA, 1998.
- [38] ASTM Standard C1240-00, *Standard Specification for Silica Fume Used in Cementitious Mixtures*, ASTM International, West Conshohocken, PA, 2000.
- [39] ASTM Standard C188-95, *Standard Test Method for Density of Hydraulic Cement*, ASTM International, West Conshohocken, PA, 1995.
- [40] ASTM Standard C204-00, *Standard Test Methods for Fineness of Hydraulic Cement by Air-Permeability Apparatus*, ASTM International, West Conshohocken, PA, 2000.
- [41] ASTM Standard C157, "Standard test method for length change of hardened hydraulic-cement mortar and concrete", *Annual Book of ASTM Standards*, 04.02 Concrete and Concrete Aggregates, 1997.
- [42] ASTM Standard C157-08, *Standard Test Method for Length Change of Hardened Hydraulic-Cement Mortar and Concrete*, ASTM International, West Conshohocken, PA, 2008.

Received: May 05, 2013

Revised: June 14, 2013

Accepted: June 18, 2013

© Al-Chaar et al.; Licensee *Bentham Open*.

This is an open access article licensed under the terms of the Creative Commons Attribution Non-Commercial License (<http://creativecommons.org/licenses/by-nc/3.0/>) which permits unrestricted, non-commercial use, distribution and reproduction in any medium, provided the work is properly cited.